

Low permeability in reinforced concrete is important to maintain structural integrity.

Slag cement reduces concrete permeability.

CONCRETE PERMEABILITY

Permeability is a measure of how easy it is for water, air and other substances such as chloride ions to enter concrete. Concrete contains pores that allow these substances to enter. Larger pores allow easier entry, while smaller pores decrease the rate at which these substances enter the concrete.

A common way to measure permeability of concrete is standard test method ASTM C1202 "Electrical Indication of Concrete's Ability to Resist Chloride Ion Penetration," also known as the rapid chloride permeability test. This method is the most accepted test to determine the relative permeability of concrete. A 60 V electrical potential is established across a sawed four inch diameter concrete cylinder section. The total current passing through the section over time and



Figure 1: Permeable concrete is a principal reason for concrete deterioration due to reinforcing steel corrosion and other deterioration mechanisms.

measured in Coulombs is reported as an indication of permeability. Lower Coulomb values indicate lower permeability. The permeability required is a function of the concrete application.

PERMEABILITY AND CHLORIDE INDUCED CORROSION

Low permeability concrete can help reduce the potential for reinforcing steel to corrode when exposed to chlorides by limiting the permeation of those chlorides into concrete. When reinforcing steel comes into contact with plastic concrete, a chemical reaction occurs between the steel and the concrete that causes a protective layer (a passive layer) to develop around the reinforcing steel. This passive layer protects against corrosion of the reinforcing steel. If the concrete is exposed to de-icing salts, these salts can migrate down to the reinforcing

steel through small pores in the concrete. Over time, the chlorides in these salts can react with the reinforcing steel, breaking down the passive layer and causing the steel to corrode. When reinforcing steel in concrete corrodes, the product of that corrosion (rust) takes up more volume than the original steel, and causes the concrete to crack. After cracks develop, the deterioration accelerates as chlorides are allowed easy ingress to the reinforcing steel. The deterioration of both the concrete and reinforcing steel compromises the integrity of the structure.


REDUCING PERMEABILITY

REDUCING PERMEABILITY WITH SLAG CEMENT

When portland cement hydrates, it forms calcium-silicate hydrate gel (CSH) and calcium hydroxide ($\text{Ca}(\text{OH})_2$). CSH is the "glue" that provides strength and holds the concrete together. Permeability is related to the proportion of CSH to $\text{Ca}(\text{OH})_2$ in the cement paste. The higher the proportion of CSH to $\text{Ca}(\text{OH})_2$, the lower the permeability of the concrete. When slag cement is used as part of the cementitious material in a concrete mixture, it reacts with $\text{Ca}(\text{OH})_2$ to form

additional CSH, which in turn lowers the permeability of the concrete. Generally, the higher the percentage of slag cement in a concrete mixture, the lower the permeability of the concrete. Concrete with lower permeability can generally be achieved by substituting between 25 to 65 percent slag cement for portland cement. Figure 2 shows the ability of a specific slag cement to reduce the permeability of concrete as measured by the rapid chloride permeability test.

Figure 2: Effect of Slag Cement on Concrete Chloride Ion Penetrability² (ASTM C1202)

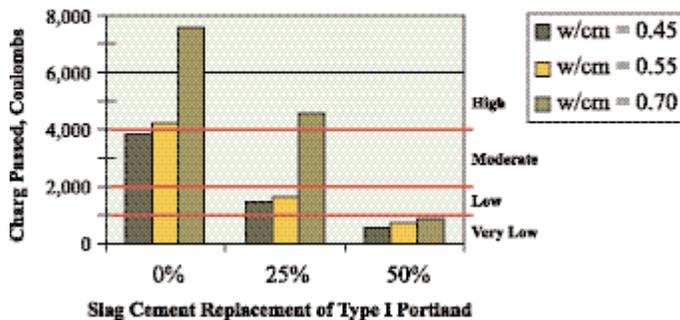

As with all concrete mixtures, trial batches should be performed to verify concrete properties. Results may vary due to a variety of circumstances, including temperature and mixture components, among other things. You should consult your slag cement professional for assistance. Nothing contained herein shall be considered or construed as a warranty or guarantee, either expressed or implied, including any warranty of fitness for a particular purpose.

References

1. ASTM C1202-97 *Standard Test Method for Electrical Indication of Concrete's Ability to Resist Chloride Ion Penetration*, American Society for Testing and Materials, West Conshohocken, PA 2001.
2. Fernandez, J and Malhotra, V. M., "Mechanical Properties, Abrasion Resistance, and Chloride Permeability of Concrete Incorporating Granulated Blast-Furnace Slag," *Cement, Concrete and Aggregates*, CCAGDP, Vol. 12, No. 2, Winter 1990.

About the Slag Cement Association...

The Slag Cement Association is the leading source of knowledge on blast-furnace slag-based cementitious products. We promote the increased use and acceptance of these products by coordinating the resources of member companies. We educate customers, specifiers and other end-users on the varied attributes, benefits and uses of these products.

The higher the percentage of slag cement in a concrete mixture, the lower the permeability of the concrete.



Slag Cement Association
38800 Country Club
Farmington Hills, MI 48331

phone: 847.977.6920
e-mail:
info@slagcement.org
web:
www.slagcement.org



Printed on recycled paper.
© 2013 Slag Cement Association